

Vibration Analysis of Composite leaf Spring

Umesh J.Jadhao¹, Dr.R.R.Deshmukh²

¹ME (CAD/CAM)Jawaharlal Nehru Engineering College, Aurangabad (MS),India

²Jawaharlal Nehru Engineering College, Aurangabad (MS),India

Abstract: Finite element analysis with full load on 3-D model of composite multi leaf spring is done using ANSYS 10 and the analytical results are compared with experimental results. Compared to steel spring, the composite leaf spring is found to have 67.35% lesser stress, 64.95% higher stiffness and 126.98% higher natural frequency than that of existing steel leaf spring. A weight reduction of 76.4% is achieved by using optimized composite leaf spring.

Keywords: Leaf Spring, Ansys, FEM etc.

I. INTRODUCTION

1.1 Leaf Spring:

Composite materials are ideal for structural application where high strength to weight and stiffness to weight ratio are required. Aircraft and spacecraft are typical weight sensitive structures in which composite materials are cost effective. Composite materials are basically hybrid materials formed of multiple materials in order to utilize their individual structural advantages in a single structural material. The composite material then has the properties of the two materials that have been combined.

The key is the macroscopic examination of a material wherein the components can be identified by the naked eye. The advantage of composite materials is that, if well designed, they usually exhibit the best qualities of their components or constituents and often some qualities that neither constituent possesses. Some of the properties that can be improved by forming a composite material are

The objective of this dissertation is to analyze experimentally and by finite element method the mechanical behavior of leaf spring made of ductile and composite material.

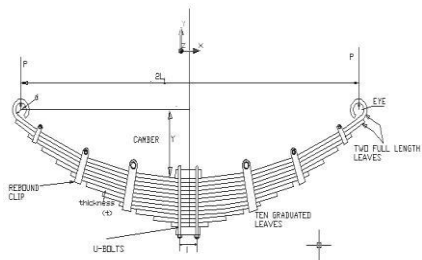


Fig. 1. Leaf spring.

Problem Definition and identification:

The present leaf spring is of Mild steel which on overloading shows bending problem. It is also found during its survey deformations induced in Mild steel springs are more. Vibrations produced by the same springs are also more which may result in failure of the spring. Also during the survey it is observed that weight of the current spring is high due to high density of mild steel which results in efficiency of vehicle.

Objectives of the work:

The suspension leaf spring is one of the potential items for weight reduction in automobiles. This project work focuses on using composite material for leaf spring of heavy vehicle for weight reduction without losing strength.

1. The objective of present dissertation is to carry out finite element analysis of composite leaf spring and experimental validation of it.
2. To study vibration characteristic of mono leaf spring.
3. To compare between steel & epoxy carbon leaf spring vibration characteristics experimentally and FEM.

Table . Stress and Deflection of existing leaf spring by Analytical Method

Sr. No.	Central load (2w) in N	Load(w) in N	Bending Stress at load w (N/mm ²)	Deflection at load w (mm)
1	1000	500	42.33	5.008
2	1500	750	63.2	7.51
3	2000	1000	84.66	10.01
4	2500	1250	105.33	12.52

II. FEM Analysis of leaf Spring

Structural Analysis of Steel Leaf Spring: Case 1: 1000 N Loads

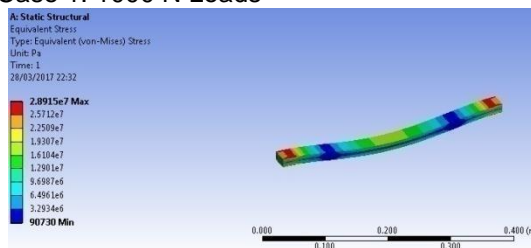


Fig. Von-Mises Stress at 1000 N

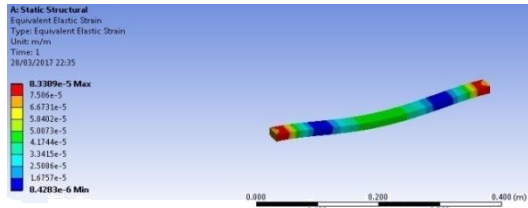


Fig. Von-Mises Strain at 1000 N

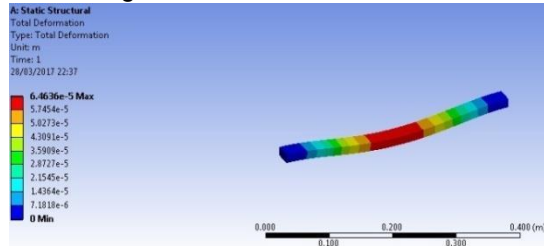


Fig.: Deformation at 1000 N

Structural Analysis of Steel Leaf Spring Table

Steel Spring	1000 N	1500N	2000N	2500N
Stress (MPa)	28.915	43.372	57.829	72.287
Strain	8.33E-5	1.25E-04	1.66E-04	1.88E-04
Deformation (mm)	6.46E-02	9.69E-02	1.29E-01	0.1616
Mass (Kg)	1.1628	1.1628	1.1628	1.1628

Stress (MPa)

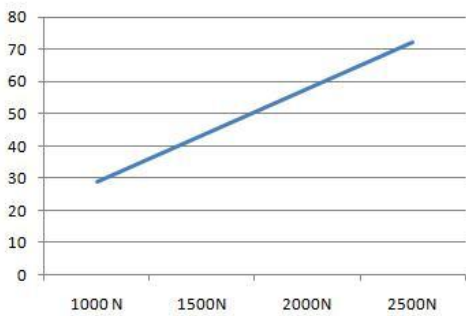


Fig.Variation of stress with load

Strain

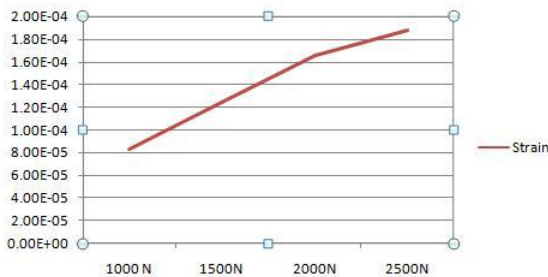


Fig.Variation of strain with load

Deformation (mm)

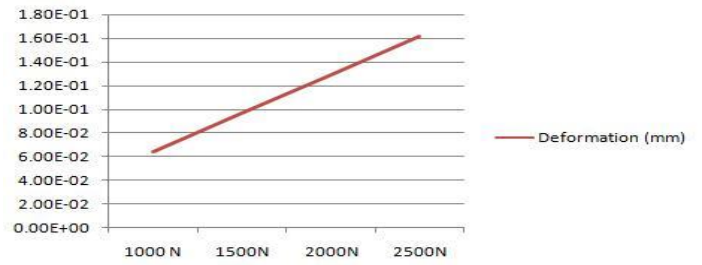


Fig.Variation of deformation with load

Structural Analysis of Carbon Fiber Spring Composite Mono Leaf Spring:

Case 1: 1000 N Load

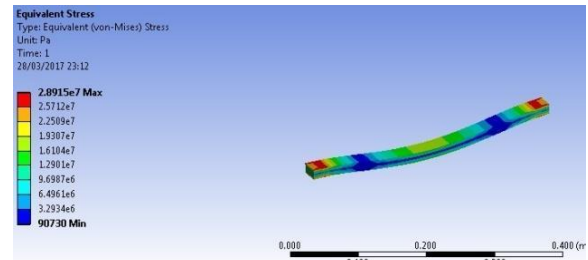


Fig. Von-Mises stress at 1000 N

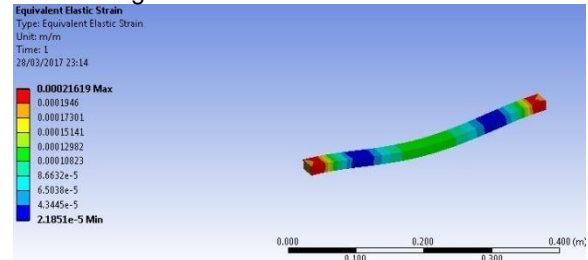


Fig .Von-Mises strain at 1000 N

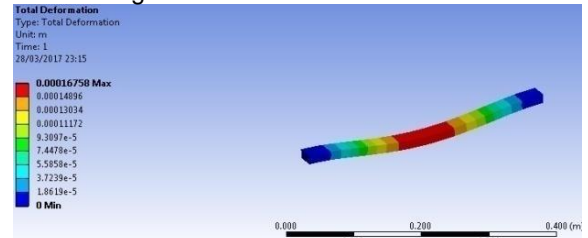


Fig .Deformation at 1000 N

Stress (MPa)

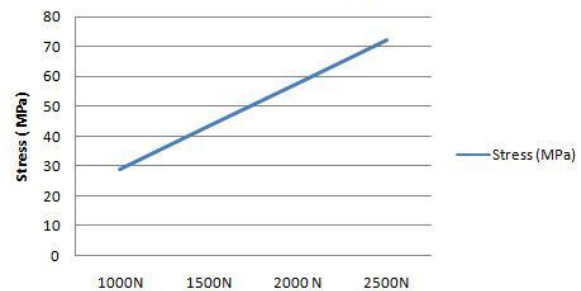


Fig.Variation of stress with load

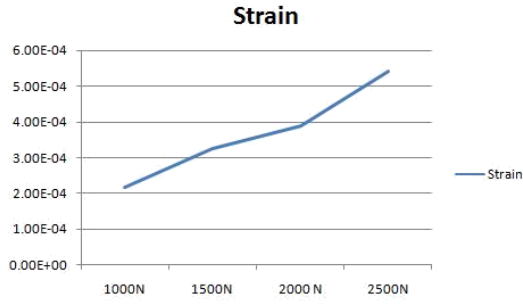


Fig.Variation of strain with load

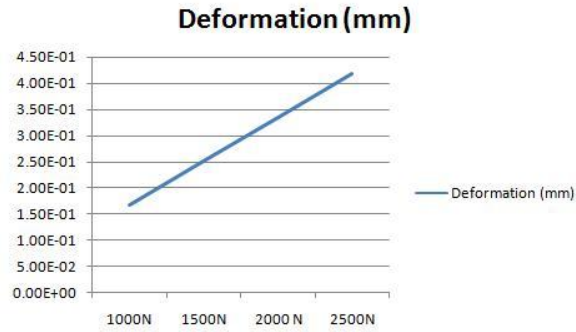


Fig.Variation of deformation with load

. Structural Analysis of E-Glass Fiber Spring Composite Mono Leaf Spring:
Case 1: 1000 N Load

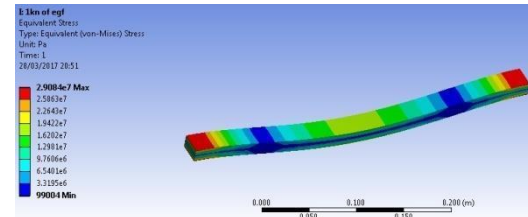


Fig.Von-Misses Stress at 1000 N

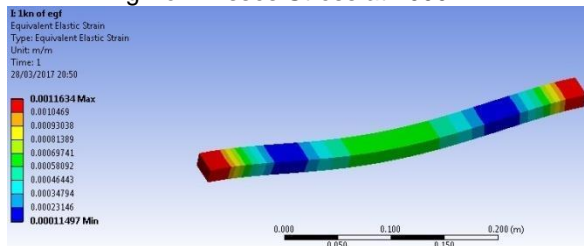


Fig. Von-Misses Strain at 1000N

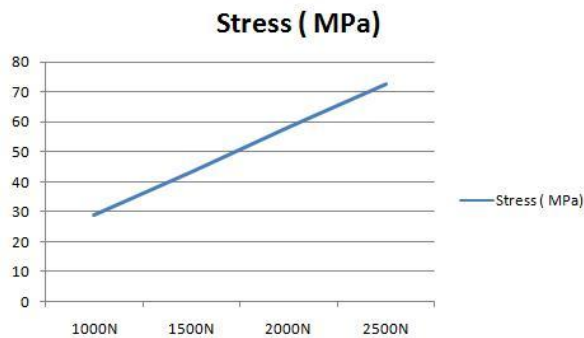


Fig. Variation of stress with load

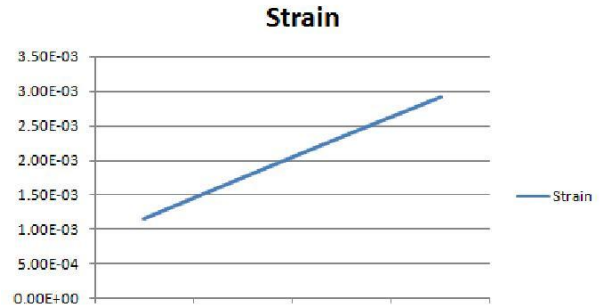


Fig.Variation of strain with load

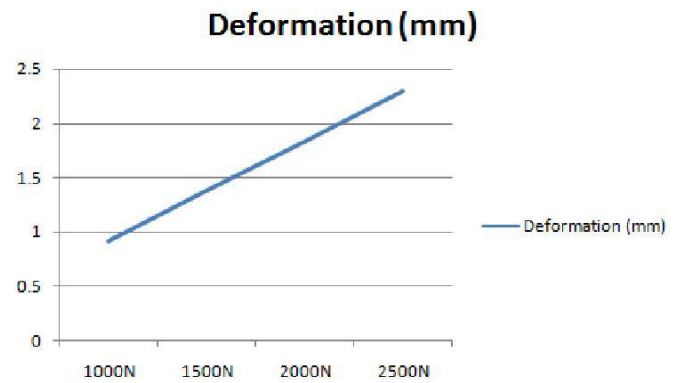


Fig.Variation of deformation with load

III.Modal Analysis

Mode shape frequency analysis of conventional leaf spring

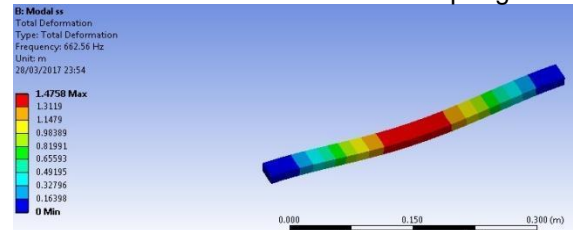


Fig . Mode 1

Mode shape frequency analysis of Carbon Fiber composite leaf spring

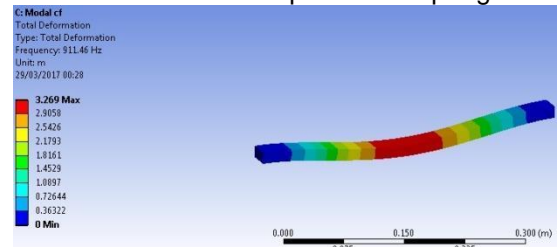


Fig.Mode 1 Mode shape frequency Analysis of E Glass fiber composite leaf spring


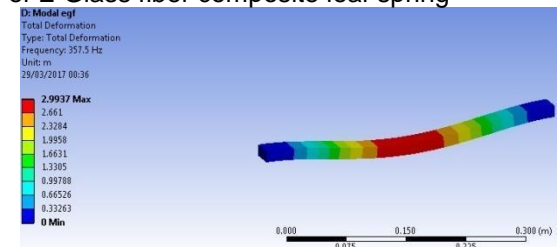


Table Modal Analysis Results Comparison
Frequency (Hz)

Modes	Steel	carbon fiber	E glass fiber
1	662.56	911.46	357.5
2	1078.7	1483.9	584.72
3	1806.2	2484.7	975.32
4	2879.3	3960.9	1563.8
5	3490.1	4801.2	1886.3
6	4427	6090	2501

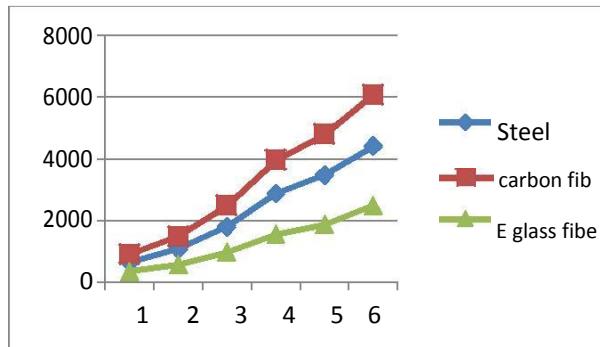

Graph Modal Analysis Results Comparison

IV. EXPERIMENTATION




Fig Loading / deflection Experimentation of carbon fiber specimen sample rod at UTM.

Loading / Deflection Experimentation of carbon fiber specimen sample rod at UTM.

Sr.No	Load (Kg)	Deflection(mm)
1	100	0.21
2	150	0.35
3	200	0.41
4	250	0.48

Table Showing comparison of experimental & FEM results of loading & deflection of carbon fiber epoxy composite material specimen rod

Sr. No	Load (N)	Deformation in mm by UTM	Deformation in mm by ANSYS
1	1000	0.21	0.16
2	1500	0.35	0.251
3	2000	0.41	0.335
4	2500	0.48	0.4184

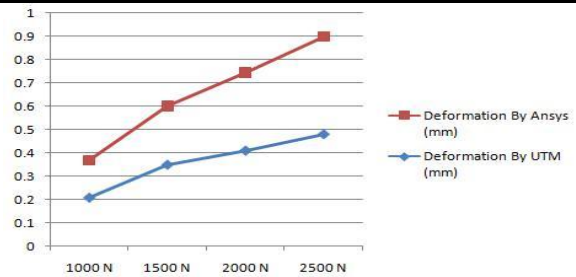

Concluding remark:

Through comparison of experimental & FEM results of loading & deflection of carbon fiber epoxy composite material specimen rod.(sample size =15 x 25 x 395 mm).Which is simply supported at both ends 50 mm away from each end. It is investigated that results are matching

with 9% error may be due to improper inputs provide to ANSYS. But still in acceptance range.

Table Showing comparison of Experimental & FEM results of natural frequency of carbon fiber epoxy composite material specimen rod

SN	Natural Frequency by FFT analyzer in HZ	Natural Frequency by ANSYS in HZ	% difference
1	927.6	911.46	5
2	1512.3	1483.9	4.5
3	2498	2484.7	5
4	3887.2	3960.9	4
5	4869.2	4801.2	3
6	6087.4	6090	1

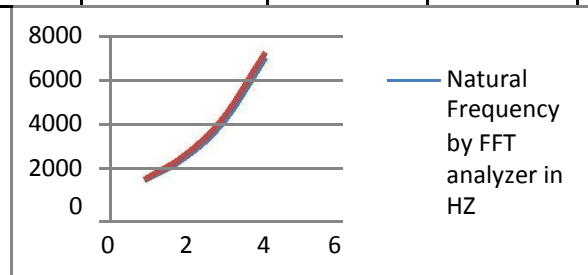


Fig.Comparative natural frequency

Concluding remark:

Through comparison of experimental & FEM results of natural frequency of carbon fiber epoxy composite material specimen rod.(sample size =15 x 25 x 395 mm). which is simply supported at both ends 50 mm away from each end. It is investigated that results are matching with 4.5% error may be due to improper inputs provided to ANSYS But still in acceptance range.

V.RESULTS AND DISCUSSION

Table Results And Discussion

Load	1000 N			1500 N		
	Steel Spring	Carbon Fiber	E-Glass Carbon Fiber	Steel Spring	Carbon Fiber	E-Glass Carbon Fiber
Stress (MPa)	28.915	28.915	29.084	43.372	43.372	43.626
Strain	5.83E-05	2.16E-04	1.16E-03	1.25E-04	3.24E-04	1.75E-03
Deformation (mm)	6.46E-02	1.68E-01	0.9124	9.69E-02	0.25136	1.3754
Mass (Kg)	1.1628	0.237	0.28144	1.1628	0.237	0.28144

Load	2000 N			2500 N		
	Steel Spring	Carbon Fiber	E-Glass Carbon Fiber	Steel Spring	Carbon Fiber	E-Glass Carbon Fiber
Stress (MPa)	57.829	57.829	58.168	72.287	72.287	72.71
Strain	1.66E-04	3.89E-04	2.33E-03	1.88E-04	5.40E-04	2.91E-03
Deformation (mm)	1.29E-01	3.35E-01	1.8339	0.1616	0.4189	2.2924
Mass (Kg)	1.1628	0.237	0.28144	1.1628	0.237	0.28144

The maximum deformations induced in Steel mono leaf spring are 6.4E-02mm, 9.69E-02, 1.29E-01, 0.1616 which is not in safe limits (1% of total span). Hence based on rigidity the design is unsafe, but if we compare deformations induced in carbon fiber for different cases it gives Minimum deformations. If we compare corresponding deformations with E-glass fiber which has more deformation. Therefore carbon fiber has good strength. The equivalent stress induced for three materials is almost same i.e.28.924 Mpa, 29.003 Mpa, 28.924 Mpa which is less than the allowable stress (380Mpa).Hence the design is safe based on strength. Corresponding weight of each lift are shown in above table. From the above table it is clear that carbon fiber has less weight as compare to other material hence weight of leaf spring optimized along with strength

VI.CONCLUSION

- 1.Experimental results of loading & deflection are matching with the FEM results hence we can replace carbon fiber leaf at steel leaf spring due to advantage of reduction of weight by 76.4 %.
- 2 .Experimental natural frequency of carbon fiber specimen rod matches with the ANSYS results with 4.5% difference which is unacceptable range.
3. Stress level is same in both the springs of steel & carbon leaf as cross section area is same.
4. Due to reduction in mass of carbon fiber leaf, suspension performance will be greater than leaf spring.
5. This carbon leaf spring will be corrosion free hence friction noise problem will be no more and no need of greasing the leaf springs as in steel leaf case.

6. Loading deflection - ANSYS results of steel leaf & carbon fiber leaf are compared and found similar with 9% of acceptable range of difference
7. Under the same static load conditions deflection and stresses of steel leaf spring and composite leaf spring are found with the great difference.
8. Deflection of Composite leaf spring is less as compared to steel leaf spring with the same loading condition

VII. REFERENCES

[1] P.Beardmore "Composite structures for automobiles", Composite Structures, HYPERLINK "http://www.sciencedirect.com/science/journal/02638223/5/3" Volume 5, Issue 3, 1986, Pages 163-176

[2] W.J.YuH.C.Kim "Double tapered FRP beam for automotive suspension leaf spring", Composite Structures, Volume 9, Issue 4, 1988, Pages 279-300

[3] Andrea Corvi,"A Preliminary Approach to Composite Beam Design using FEM Analysis", Composite Structure 1990, (16), (5), pp. 279–300.

[4] Erol Sancaktar,"Design, Analysis, and Optimization of composite leaf spring for light vehicle application", Composite structure 1999, (44), pp. 195-204.

[7] Siddaramanna Gular Shiva Shankar, Vijayarangan,"Mono Composite Leaf Spring for Light Weight Vehicle Design", End Joint Analysis and Testing. Journal of Materials Science 2006, (12), (8), pp. 220-225.

[8] Mahdi, E. O.M.S. Alkoles, A.M.S. Hamouda, B.B. Sahari,"Light Composite Elliptic Springs for Vehicle Suspension", Journal of composite structure 2006, (75), pp. 24-28.

[9] Ahemad F.N. Refngah, S. Abdullah, A. Jalar, L. B. Chua,"Life Assessment of a Parabolic Spring under Cyclic Strain Loading", European Journal of Scientific Research 2009, 28 ,(3), pp. 351-363.

[10] Arora, Vinkel M.L. Aggarwal, Gian Bhisnan,"A Comparative Study of Leaf Springs in Automotive Vehicles", International Journal of Engineering Science and Technology 2012, 3 (9), pp. 6856-6866.

[11] Ashok Kumar T.N.et.al,"Design and Material Optimization of Heavy Vehicle Leaf Spring International Journal of Research in Mechanical Engineering & Technology", Vol. 4, Issue 1, April 2014, pp. 80-88.

[12] Aher, V. K. Mr. Sonawane P. M, "Static and Fatigue Analysis of Multi Leaf Spring used in the suspension System of LCV", International Journal of Engineering Research and Applications (IJERA), Vol. 2, Issue 4, July-August 2012, pp.1786-1791.

[13] Avani B. Londhe,"FEA and Analytical Analysis of NaturalFibers Composite Leaf Spring", International Journal of Mechanical Engineering and Research, Vol. 3, No. 4, 2013,

pp. 355-360.

[14] Badugu Karthik, Sathaiah Gajam et.al, "Manufacturing of Fiber Glass & Development, Static Load Testing, Analysis of Composite Leaf Spring", International Journal of Emerging

Technology and Advanced Engineering, Vol. 3, Issue 9, September 2013, pp. 155-161.

[15] Beardmore P, Johnson CF., "The potential for composites in Structural automotive applications", Comp Science and Technology 1986, (26), pp. 251-81.

[16] Banakar, Prashant H. K. Shivanand, H. B. Nirajan. Mechanical Properties of Angle Ply Laminated Composite - A Review", International Journal of Pure and Applied Science and Technology 2012, 9(2), (30), pp. 127-133.

[17] Badkar Prahalad Sawant , "Design Improvements of Leaf Spring of BEML Tatra 815 VVNC 8 X 8 Truck", International Journal of Emerging Technology and Advanced Engineering 2013, 3(1), pp. 318-324

[18] Cherruault J.Y., Hou, J.P , Nairna I., G. Jeronimidis, R. M. Mayer, "Evolution of the Eye-End Design of a composite leaf spring for Heavy Axle Loads", Journal of Composite Structures 2007, (78), (13), pp. 351-358.

[19] Daugherty R.L., "Composite leaf spring in heavy truck application", Composite Material Proceedings of Japan-US Conference Tokyo 1981, pp. 529-538.

[20] Dara Ashok, M.V Mallikarjun, Venkata Ramesh Mamilla, "Design and Structural Analysis of Composite Multi Leaf Spring", International Journal of Emerging trends in Engineering and Development 2012, 5 (2), pp. 30-37.

[21] Dubey D.N., Mahakalkar S.G, "Stress Analysis of a Monoparabolic Leaf Spring: A Review", International Journal of Modern Engineering Research (IJMER) Vol. 3, Issue 2, March-April 2013, pp. 769-772.

[22] Gebremeskel Shishhay Amare, "Design, simulation and prototyping of single composite spring for light weight vehicle 2012", 12

[23] Gaikwad Dadasaheb, Sonkusare, Rakhi Sameer Wagh, "Composite Leaf Spring for Light Weight Vehicle- Materials, Manufacturing Process", Advantages & Limitations Int J Engg Techsci, Vol. 3(2) 2012, pp. 410-413

[24] Joo-Teck Jeffery Kuch, Tarlochan Faris, "Finite Element analysis on the Static and Fatigue characteristics of Composite Multi-leaf Spring", Journal of Applied Physics and Engineering 2012, 13 (3), pp. 159-164.

[25] Helmen D. Devaraj, M. Venkatesan, "Static Analysis of Composite Semi – Elliptical Leaf Spring IOSR", Journal of Engineering Apr. 2012, Vol. 2(4) pp. 598-603

[26] Karthik. Badugu, Sathaiah.Gajam, B. Mahasenadhipathi Rao, "Manufacturing of Fiber

Glass & Development, Static Load Testing, Analysis of Composite Leaf Spring", International Journal of Emerging Technology and Advanced Engineering, Vol. 3, Issue 9, September 2013, 155.

[27] Kumar Krishanan, M.L. Aggarwal, "Computer Aided FEA Comparison of Mono Steel and Mono GRP Leaf Spring", International Journal of Advance Engineering Research and Studies 2012, 1(11), pp. 155-158

[28] Kumar M. Senthil, S. Vijayarangan, "Analytical and Experimental Studies on Fatigue Life Prediction of Steel and Composite Multi-leaf Spring for Light Passenger Vehicles", Journal of scientific and Industrial research 2007, (66), (10), pp. 128-134.